


TECHNICAL DATA SHEET



V5.5



PolyLite™ PC Transparent


PolyLite™ PC is produced using a polycarbonate resin specifically engineered for 3D printing. It delivers good stiffness and heat resistance with light diffusing properties.

WWW.POLYMAKER.COM

PHYSICAL PROPERTIES

PROPERTY	TESTING METHOD	TYPICAL VALUE
Density	ISO1183, GB/T 1033	1.19 g/cm ³ at 23°C
Melt index	260°C, 2.16kg	8-11 g/10min
Light transmission	GB/T 2410	89%
Flame retardancy	N/A	N/A


MOISTURE ABSORPTION CURVE

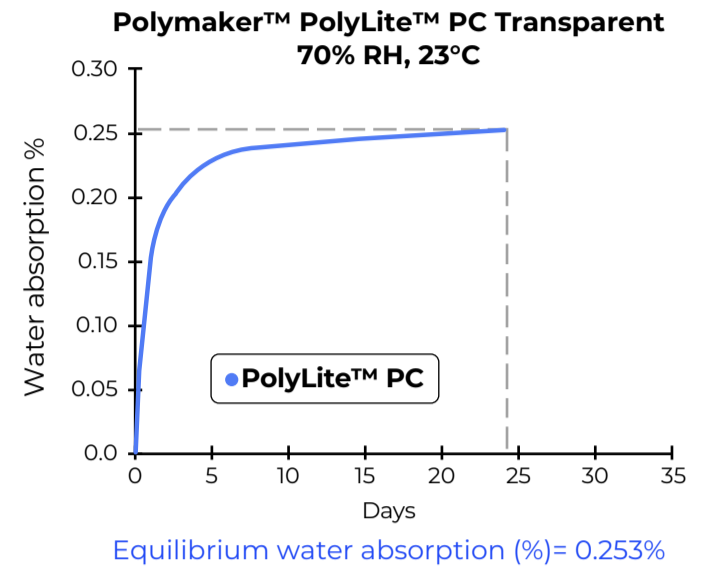

THERMAL PROPERTIES

PROPERTY	TESTING METHOD	TYPICAL VALUE
Glass transition temp.	DSC, 10°C/min	113°C
Melting temp.	DSC, 10°C/min	N/A
Crystallization temp.	DSC, 10°C/min	N/A
Decomposition temp.	TGA, 20°C/min	>360°C
Vicat softening temp.	ISO 306, GB/T 1633	120°C
Heat deflection temp.	ISO 75 1.8MPa	107°C
Heat deflection temp.	ISO 75 0.45MPa	111°C

HDT CURVE

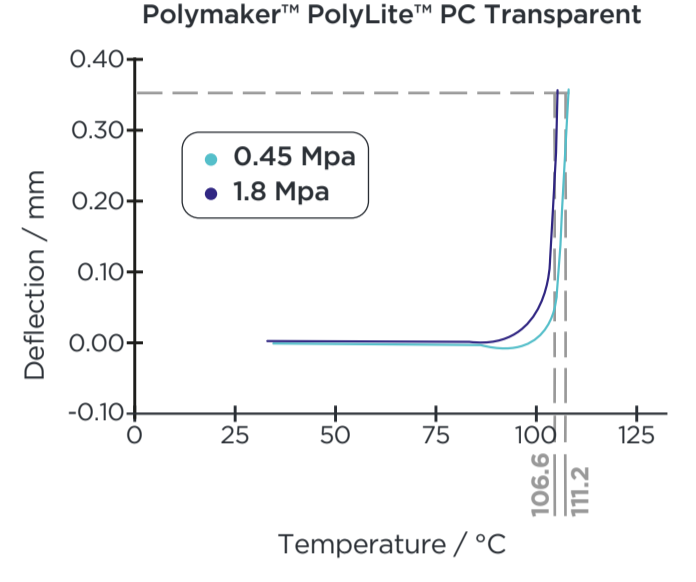

MECHANICAL PROPERTIES

PROPERTY	TESTING METHOD	TYPICAL VALUE
Young's modulus (X-Y)	ISO 527, GB/T 1040	2497 ± 154 MPa
Young's modulus (Z)		2371 ± 55 MPa
Tensile strength (X-Y)	ISO 527, GB/T 1040	69.1 ± 3.0 MPa
Tensile strength (Z)		52.8 ± 1.7 MPa
Elongation at break (X-Y)	ISO 527, GB/T 1040	4.8 ± 0.9 %
Elongation at break (Z)		2.7 ± 0.1 %
Bending modulus (X-Y)	ISO 527, GB/T 1040	2640 ± 47 MPa
Bending modulus (Z)		N/A
Bending strength (X-Y)	ISO 527, GB/T 1040	106.1 ± 1.6 MPa
Bending strength (Z)		N/A
Notched charpy impact strength (X-Y)	ISO 179, GB/T 1043	4.1 ± 0.9 kJ/m ²

CHEMICAL RESISTANCE DATA

PROPERTY	TYPICAL VALUE
Effect of weak acids	Good
Effect of strong acids	Poor
Effect of weak alkalis	Fair
Effect of strong alkalis	Poor
Effect of oils and grease	Good

Good:
Material may get minor attack after long periods of storage with chemical at ambient temperature

Fair:
Material can be used for short time contact with chemicals at ambient temperature

Poor:
Material becomes unstable on contact with chemical at ambient temperature

RECOMMENDED PRINTING CONDITIONS

Nozzle temperature	245-270°C
Build plate temperature	90-105°C
Build surface treatment	PC and Textured PEI
Cooling fan	OFF
Closure chamber	Needed (70°C-100°C)

Printing speed	50-200mm/s
Drying temp. and time	75°C/6H
Retraction distance	1-3 (mm)
Retraction speed	20-40 (mm/s)

*Based on 0.4mm nozzle. Printing conditions may vary with different nozzle diameters.

NOTE:
- When printing with PolyLite™ PC, it is recommended to use an enclosure. For large part, it is recommended to use a heated chamber.
- It is recommended to anneal the printed part right after the printing process to release the residual internal stress.
Annealing settings: 90°C for 2h



PolyBox™ or PolyDryer™ Box

NOTE

It is highly recommended to use the PolyBox™ or PolyDryer™ Box when printing or storing.



HOW TO MAKE SPECIMENS

Printing temperature	260°C
Bed temperature	100°C
Top & bottom layer	3
Environmental Temperature	90°C

Infill	100%
Shell	2
Cooling fan	OFF



FLEXURAL TESTING SPECIMEN

ISO 178, GB/T 9341

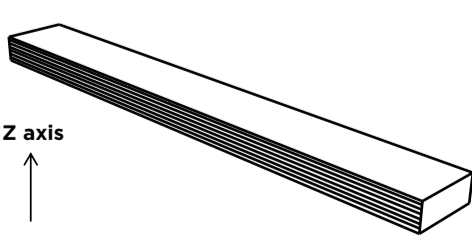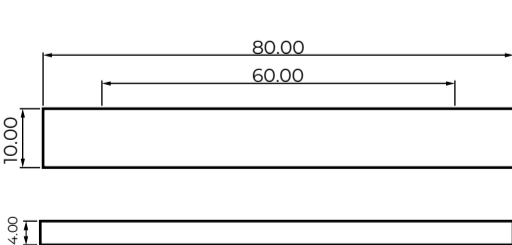



TENSILE TESTING SPECIMEN

ISO 527, GB/T 1040

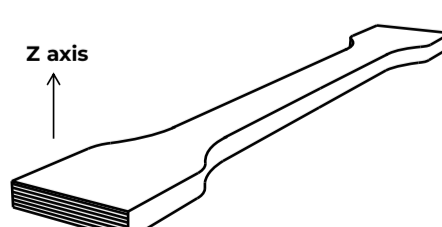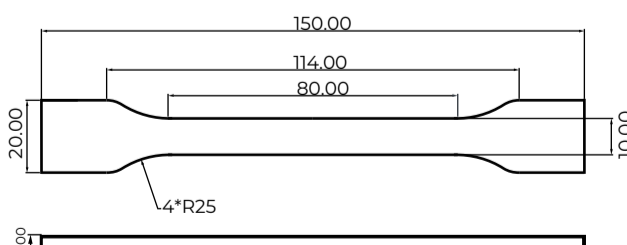

IMPACT TESTING SPECIMEN

ISO 179, GB/T 1043

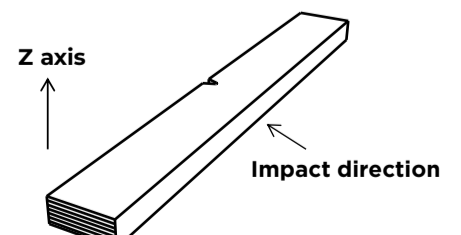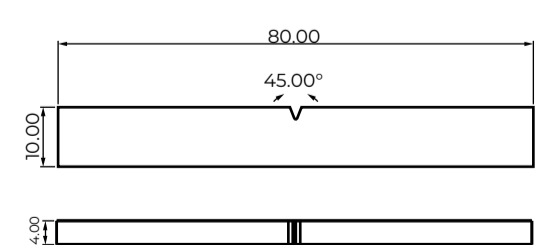

*Based on testing with Polymaker™ PolyLite™ PC Transparent (SKU: PC01001)

DISCLAIMER

The typical values presented in this data sheet are intended for reference and comparison purposes only. They should not be used for design specifications or quality control purposes. Actual values may vary significantly with printing conditions. End-use performance of printed parts depends not only on materials, but also on part design, environmental conditions, printing conditions, etc. Product specifications are subject to change without notice. Each user is responsible for determining the safety, lawfulness, technical suitability, and disposal/recycling practices of Polymaker™ materials for the intended application. Polymaker™ makes no warranty of any kind, unless announced separately, to the fitness for any use or application. Polymaker™ shall not be made liable for any damage, injury or loss induced from the use of Polymaker™ materials in any application.